

# TEST REPORT

**CUSTOMER:** Enviroplaz  
PO Box 38860  
Howick 2145  
Auckland

**CUSTOMER REFERENCE:** Peter Barrow

**TEST SPECIFICATION:** AS/NZS 3661.1:2003 Slip resistance of pedestrian surfaces  
Appendix A- method for the measurement of the coefficient of friction of wet surfaces

**ITEM TESTED:** Five (5) Plastic samples  
ID: HY Tread

**DATE OF TEST:** 02 May 2014

**RESULTS:** Refer to the body of this report.

The attention of the client is drawn to the Terms and Conditions, which form part of the terms of engagement between SAI Global (NZ) Limited and the client. To access our terms and conditions please use the link below.

<http://www.saiglobal.com/product-certification/downloads/ProductTestingTsandCs-Imtest.pdf>

**Compiled By:**  
W P Morris



**Checked By:**  
J H Kelly



### Synopsis:

Five plastic "HY Tread" samples were submitted to determine the co-efficient of friction in accordance with appendix A for wet surfaces.



Figure 1. Items tested.

### Results:

Sample	BPN Reading (wet)					Average (Of last 3 readings)	Co-efficient of friction
	1	2	3	4	5		
1	44	43	43	43	43	43	<b>0.45</b>
2	44	43	42	42	42	42	<b>0.44</b>
3	44	44	43	43	43	43	<b>0.45</b>
4	43	44	44	44	44	44	<b>0.46</b>
5	44	43	43	43	43	43	<b>0.45</b>

Table 1

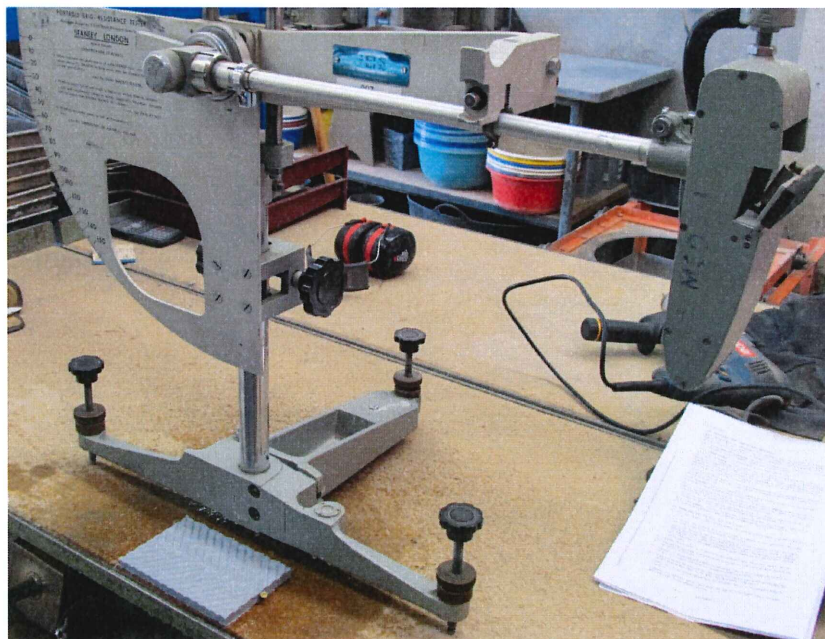


Figure 2. Pendulum friction tester.